



Standard Test Methods for Plane-Strain Fracture Toughness and Strain Energy Release Rate of Plastic Materials¹

This standard is issued under the fixed designation D 5045; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope *

1.1 These test methods are designed to characterize the toughness of plastics in terms of the critical-stress-intensity factor, K_{Ic} , and the energy per unit area of crack surface or critical strain energy release rate, G_{Ic} , at fracture initiation.

1.2 Two testing geometries are covered by these test methods, single-edge-notch bending (SENB) and compact tension (CT).

1.3 The scheme used assumes linear elastic behavior of the cracked specimen, so certain restrictions on linearity of the load-displacement diagram are imposed.

1.4 A state-of-plane strain at the crack tip is required. Specimen thickness must be sufficient to ensure this stress state.

1.5 The crack must be sufficiently sharp to ensure that a minimum value of toughness is obtained.

1.6 The significance of these test methods and many conditions of testing are identical to those of Test Method E 399, and, therefore, in most cases, appear here with many similarities to the metals standard. However, certain conditions and specifications not covered in Test Method E 399, but important for plastics, are included.

1.7 This protocol covers the determination of G_{Ic} as well, which is of particular importance for plastics.

1.8 These test methods give general information concerning the requirements for K_{Ic} and G_{Ic} testing. As with Test Method E 399, two annexes are provided which give the specific requirements for testing of the SENB and CT geometries.

1.9 Test data obtained by these test methods are relevant and appropriate for use in engineering design.

1.10 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

NOTE 1—There is currently no ISO standard that duplicates these test methods. Pending ISO/CD 13586 covers similar testing and references this test method for testing conditions.

¹ These test methods are under the jurisdiction of ASTM Committee D-20 on Plastics and is the direct responsibility of Subcommittee D20.10 on Fracture Mechanics.

Current edition approved March 10, 1999. Published June 1999. Originally published as D 5045 – 90. Last previous edition D 5045 – 96.

2. Referenced Documents

2.1 ASTM Standards:

D 638 Test Method for Tensile Properties of Plastics²

D 4000 Classification System for Specifying Plastic Materials³

E 399 Test Method for Plane-Strain Fracture Toughness of Metallic Materials⁴

E 691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method⁵

3. Terminology

3.1 Definitions:

3.1.1 *compact tension, n*—specimen geometry consisting of single-edge notched plate loaded in tension. See 3.1.5 for reference to additional definition.

3.1.2 *critical strain energy release rate, G_{Ic} , n*—toughness parameter based on energy required to fracture. See 3.1.5 for reference to additional definition.

3.1.3 *plane-strain fracture toughness, K_{Ic} , n*—toughness parameter indicative of the resistance of a material to fracture. See 3.1.5 for reference to additional definition.

3.1.4 *single-edge notched bend, n*—specimen geometry consisting of center-notched beam loaded in three-point bending. See 3.1.5 for reference to additional definition.

3.1.5 Reference is made to Test Method E 399 for additional explanation of definitions.

3.2 Definitions of Terms Specific to This Standard:

3.2.1 *yield stress, n*—stress at fracture is used. The slope of the stress-strain curve is not required to be zero. See 7.2 for reference to additional definition.

4. Summary of Test Methods

4.1 These test methods involve loading a notched specimen that has been precracked, in either tension or three-point bending. The load corresponding to a 2.5 % apparent increment of crack extension is established by a specified deviation from the linear portion of the record. The K_{Ic} value is calculated from this load by equations that have been established on the basis of elastic stress analysis on specimens of the

² Annual Book of ASTM Standards, Vol 08.01.

³ Annual Book of ASTM Standards, Vol 08.02.

⁴ Annual Book of ASTM Standards, Vol 03.01.

⁵ Annual Book of ASTM Standards, Vol 14.02.

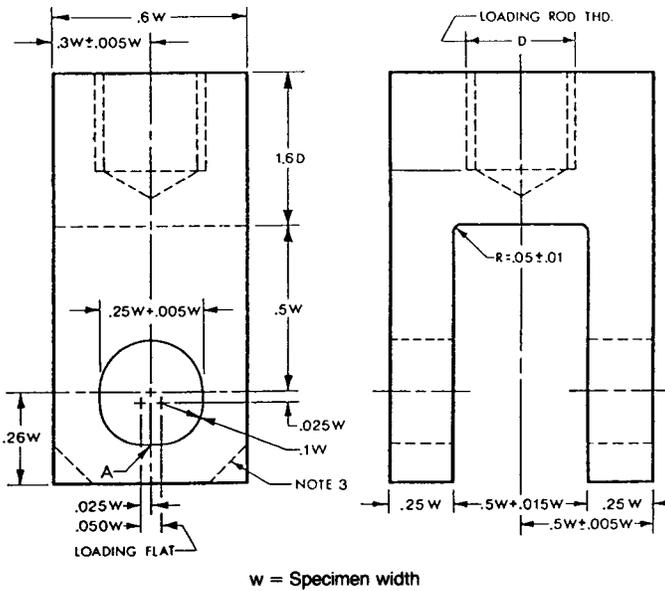


FIG. 2 Tension Testing Clevis Design for CT

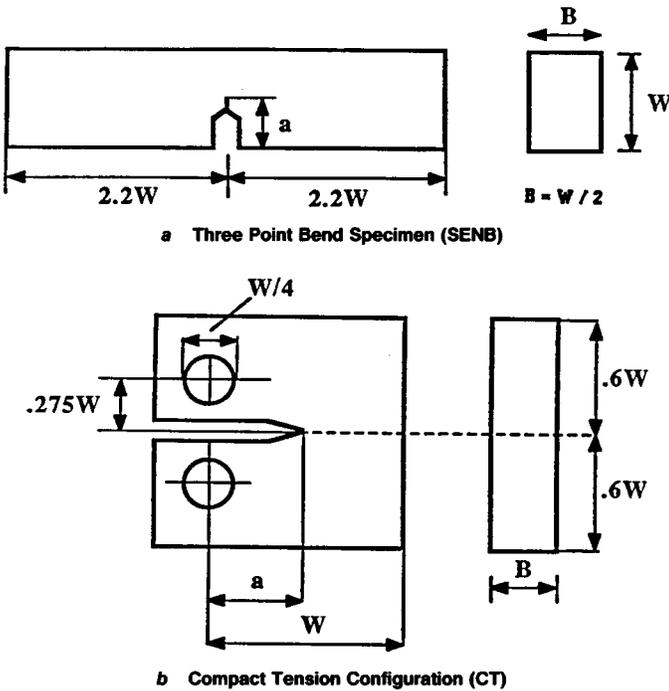


FIG. 3 Specimen Configuration as in Test Method E 399

to these test methods, the following size criteria must be satisfied:

$$B, a, (W - a) > 2.5 (K_Q/\sigma_y)^2 \quad (1)$$

where:

K_Q = the conditional or trial K_{Ic} value (see Section 9), and σ_y = the yield stress of the material for the temperature and loading rate of the test.

The criteria require that B must be sufficient to ensure plane strain and that $(W - a)$ be sufficient to avoid excessive plasticity in the ligament. If $(W - a)$ is too small and non-linearity in loading occurs, then increasing the W/B ratio to a maximum of 4 can be attempted for SENB specimens.

7.2 Yield Stress:

7.2.1 The yield stress, σ_y , is to be taken from the maximum load in a uniaxial tensile test. The yield-stress test can be performed in a constant stroke-rate uniaxial tensile test where the loading time to yield is within $\pm 20\%$ of the actual loading time observed in the fracture test. The definition of yield stress is not identical to that found in Test Method D 638 which requires a zero slope to the stress-strain curve. If it is established that $2.5 (K_Q/\sigma_y)^2$ is substantially less than the specimen thickness employed, then a correspondingly smaller specimen can be used.

7.2.2 Yielding in tensile tests in most polymers can be achieved by carefully polishing the specimen sides. If yielding does not occur and brittle fracture is observed, the stress at fracture may be used in the criteria to give a conservative size value.

7.2.3 If a tensile test cannot be performed, then an alternative method is to use 0.7 times the compressive yield stress.

7.2.4 If the form of the available material is such that it is not possible to obtain a specimen with both crack length and thickness greater than $2.5 (K_{Ic}/\sigma_y)^2$, it is not possible to make a valid $K_{Ic}(G_{Ic})$ measurement according to these test methods.

7.2.5 The test method employed for determining yield stress, as mentioned in 7.2.1-7.2.4, must be reported.

7.3 Specimen Configurations:

7.3.1 *Standard Specimens*—The configurations of the two geometries are shown in Fig. 3(a) (SENB) and Fig. 3(b) (CT), which are taken from Annexes A3 and A4, respectively, of Test Method E 399. The crack length, a (crack prenotch plus razor notch), is nominally equal to the thickness, B , and is between 0.45 and 0.55 times the width, W . The ratio W/B is nominally equal to two.

7.3.2 *Alternative Specimens*—In certain cases it may be desirable to use specimens having W/B ratios other than two. Alternative proportions for bend specimens are $2 < W/B < 4$. This alternative shall have the same a/W and S/W ratios as the standard specimens (S = support span).

7.3.3 *Displacement Correction Specimens*—Separately prepared unnotched specimen configurations for the determination of the displacement correction mentioned in 9.2 are shown in Fig. 4(a) for SENB and in Fig. 4(b) for CT configurations, respectively.

7.4 Specimen Preparation:


7.4.1 Initially, prepare a sharp notch by machining. Subsequently, initiate a natural crack by inserting a fresh razor blade and tapping. If a natural crack cannot be successfully initiated by tapping, a sufficiently sharp crack can alternatively be generated by sliding or sawing a new razor blade across the notch root. The procedure is given in 7.4.1.1-7.4.1.5.

7.4.1.1 Machine or saw a sharp notch in the specimen and generate a natural crack by tapping on a fresh razor blade placed in the notch.

7.4.1.2 The depth of the natural crack generated by tapping must be at least two times longer than the width of the sawed-in slot or the machined notch tip radius (notch diagram in Fig. 3 is not to scale).

7.4.1.3 If a natural crack cannot be successfully generated, either because the specimen fractures during tapping, as in

a) Single edge notch bend

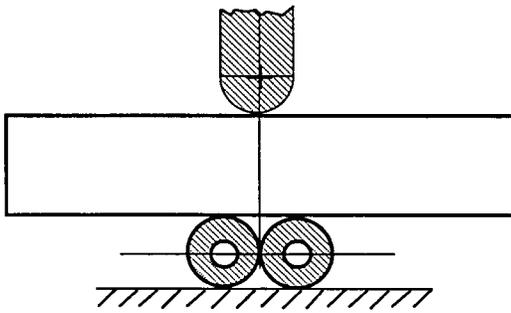

b) Compact Tension

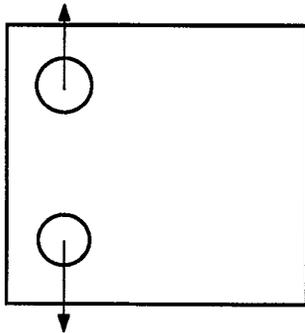


FIG. 4 Arrangements for Finding Indentation Displacement

some brittle materials, or because a crack cannot be seen, as in some tough materials, then a fresh razor blade can be slid in one motion, or with a sawing motion across the machined notch.

7.4.1.4 The depth of the razor notch generated by sliding the razor blade must be two times longer than the width of the sawed-in slot or of the pre-notch tip radius (the notch diagram in Fig. 3 is not to scale).

NOTE 2—Pressing the blade into the notch is not recommended for more ductile resins because it may induce residual stresses at the crack tip which can give an artificially high value of K_{Ic} .

7.4.1.5 The total depth of the notch obtained by machining and generation of the natural crack is the crack length, a .

8. General Procedure

8.1 Number of Tests—It is recommended that at least three replicate tests be made for each material condition.

8.2 Specimen Measurement—Specimen dimensions shall conform to those shown in Fig. 3(a, b). Three fundamental measurements are necessary for the calculation of K_{Ic} and G_{Ic} , namely, the thickness, B , the crack length, a , and the width W .

8.2.1 Measure the thickness, B , to 0.1 % accuracy at not less than three positions. The average of these three measurements should be recorded as B .

8.2.2 Measure the crack length a , after fracture to the nearest 0.5 % accuracy at the following three positions: at the center of the crack front, and the end of the crack front on each surface of the specimen. Use the average of these three measurements as the crack length, a .

8.2.3 Measure the width, W , to within 0.1 % as described in the annex appropriate to the specimen type being tested.

8.3 Loading Rate:

8.3.1 Since plastics are viscoelastic materials, it is necessary to specify both the temperature and time scale under which the result was obtained. As a basic test condition it is recommended that a temperature of 23°C, and a crosshead rate of 1.67×10^{-4} m/s (10 mm/min) be used. Both loading rate and loading time should be noted on the report form.

NOTE 3—If it is not possible to obtain valid results at 23°C, it is often possible to do so by decreasing the temperature which usually does not change K_{Ic} greatly but increases the yield stress, rendering the fracture more brittle.

8.3.2 It is recommended that speeds greater than 1 m/s or loading times less than 1 ms should be avoided because of the risk of dynamic effects causing errors.

8.4 Loading—The test is performed and the load versus loading-point displacement curve obtained. In the ideal case this is a linear diagram with an abrupt drop of load to zero at the instant of crack growth initiation. In some cases this occurs and K_Q can be found from the maximum load.


8.5 Load-Displacement Area—A procedure for determining G_{Ic} is included in 9.3. This requires an accurate integration of the load versus loading point displacement curve, which necessitates an accurate displacement determination using a displacement transducer. A cross check on the accuracy of G_{Ic} is provided through a corrected compliance.

9. Calculation and Interpretation of Results

9.1 Interpretation of Test Record and Calculation of K_Q —In order to establish that a valid K_{Ic} has been determined, it is first necessary to calculate a conditional result, K_Q , which involves a construction on the test record, and to then determine whether this result is consistent with the size of the specimen in accordance with 9.1.3. The procedure is given in 9.1.1-9.1.5.

9.1.1 Load the specimen and obtain a diagram as shown in Fig. 5. Draw a best straight line (AB) to determine the initial compliance, C . C is given by the reciprocal of the slope of line (AB). Draw a second line (AB') with a compliance 5 % greater than that of line (AB). If the maximum load that the specimen was able to sustain, P_{max} , falls within lines (AB) and (AB'), use P_{max} to calculate K_Q . If P_{max} falls outside line (AB) and line (AB'), then use the intersection of line (AB') and the load curve as P_Q . Furthermore, if $P_{max}/P_Q < 1.1$, use P_Q in the calculation of K_Q . However, if $P_{max}/P_Q > 1.1$, the test is invalid.

9.1.2 Calculate K_Q in accordance with the procedure given in A1.4 for SENB and A2.5 for CT. For this calculation, a value of a , which is the total crack length after both notching and pre-cracking, but before fracture, is best determined from the fracture surface after testing. An average value is used, but the difference between the shortest and longest length should not exceed 10 %. Take care that it is the original crack which is

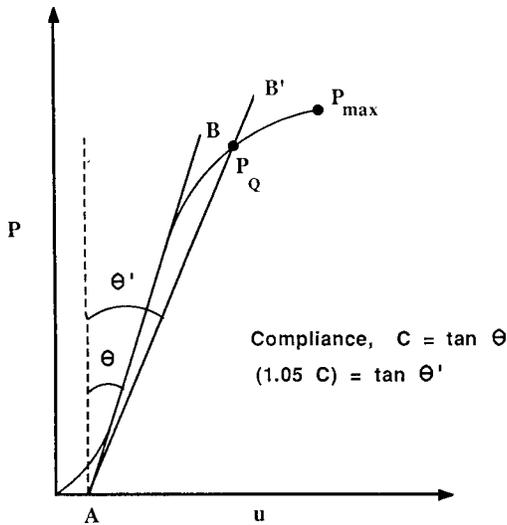

NOTE 1—C is the inverse slope of line AB.

FIG. 5 Determination of C and P_Q

being observed, since slow growth can occur prior to catastrophic fast fracture.

9.1.3 Check the validity of K_Q via the size criteria. Calculate $2.5 (K_Q/\sigma_y)^2$ where σ_y is the yield stress discussed in 7.2.1. If this quantity is less than the specimen thickness, B , the crack length, a , and the ligament ($W - a$), K_Q is equal to K_{Ic} . Otherwise the test is not a valid K_{Ic} test.

NOTE 4—Note that use of a specimen with too small a thickness, B , will result in K_Q being higher than the true K_{Ic} value while a small ($W - a$) will result in a K_Q value that is lower than the true K_{Ic} value. The net effect may be close to the correct K_{Ic} but unfortunately in an unpredictable way, since the dependence on B cannot be quantified.

9.1.4 For the recommended specimen dimensions of $W = 2B$ and $a/W = 0.5$, all the relationships of 9.1.3 are satisfied simultaneously. In fact, the criterion covers two limitations in that B must be sufficient to ensure plane strain, but ($W - a$) has to be sufficient to avoid excessive plasticity in the ligament. If ($W - a$) is too small the test will often violate the linearity criteria. If the linearity criterion is violated, a possible option is to increase W for the same a/W and S/W ratios. Values of W/B of up to 4 are permitted.

9.1.5 If the test result fails to meet the requirements in either 9.1.1 or 9.1.3, or both, it will be necessary to use a larger specimen to determine K_Q . The dimensions of the larger specimen can be estimated on the basis of K_Q , but generally must be increased to 1.5 times those of the specimen that failed to produce a valid K_{Ic} value.

9.2 Displacement Correction for Calculation of G_Q —Make a displacement correction for system compliance, loading-pin penetration, and sample compression, then obtain G_{Ic} from the energy derived from integration of the load versus load-point displacement curve.

9.2.1 The procedure for obtaining the corrected displacement, $u_c(P)$, at load P from the measured displacement, $u_Q(P)$, is as follows: Use an uncracked calibration specimen, as shown in Fig. 4(a) for SENB samples and Fig. 4(b) for CT samples as mentioned in 7.3.3. Load these specimens and determine the load-displacement curve, giving $u_i(P)$. The corrected displacement

is then given as $u_c(P) = u_Q(P) - u_i(P)$ for both the SENB and CT geometries.

9.2.2 In practice, a displacement-correction curve that is linear can usually be obtained (up to the maximum loads recorded in the fracture test), and this simplifies the displacement correction to be applied to the fracture test. Initial non-linearity due to penetration of the loading pins into the specimen should occur during both the calibration test and the actual fracture test. Linearization of the near-zero correction data and the fracture test data can compensate for this initial non-linearity.

9.2.3 The displacement correction must be performed for each material and at each test temperature or rate. Polymers are generally temperature- and rate-sensitive and the degree of loading-pin penetration and sample compression can vary with changes in these variables.

9.2.4 The indentation tests should be performed in such a way that the loading times are the same as the fracture tests. Since the indentations are stiffer, this will involve lower rates to reach the same loads.

9.3 Calculation of G_Q —In principle, G_{Ic} can be obtained from the following:

$$G_{Ic} = \frac{(1 - \nu^2)K_{Ic}^2}{E} \quad (2)$$

but for plastics, E must be obtained at the same time and temperature conditions as the fracture test because of viscoelastic effects. Many uncertainties are introduced by this procedure and it is considered preferable to determine G_{Ic} directly from the energy derived from integration of the load versus displacement curve up to the same load point as used for K_{Ic} and shown in Fig. 6(a, b).

9.3.1 The energy must be corrected for system compliance, loading-pin penetration, and sample compression. This is done by correcting the measured displacement values, as shown in Fig. 6(a, b). Accordingly, if complete linearity is obtained, one form of the integration for energy is as $U = \frac{1}{2}P_Q[u_Q - u_i]$, where P_Q is defined in 9.1.1.

9.3.2 Alternatively, it is possible to use the integrated areas from the measured curve, U_Q , of Fig. 6(a) and indentation curves, U_i , of Fig. 6(b) in accordance with the following:

$$U = U_Q - U_i \quad (3)$$


9.3.3 Calculate G_Q from U in accordance with the procedure given in A1.4.4 for SENB and in A2.6 for CT.

9.3.4 A useful cross check on accuracy may be made using the tensile modulus, E , and Poisson's ratio, ν . $E/(1 - \nu^2)$ can be found from the corrected compliance, C_c , using the following:


$$[E/(1 - \nu^2)]BC_c = 2f^2\phi = \Psi \quad (4)$$

in SENB. The factors f , ϕ , and Ψ are given in Table 1 and Table 2 for the two geometries. This value of $E/(1 - \nu^2)$ may be compared with that obtained from K_{Ic}^2/G_{Ic} . The former value should be the larger, but the difference should be <15%. The corrected compliance, C_c , is obtained from the measured compliance in the fracture test, C_Q , and the compliance from the indentation test, C_i , in accordance with the following:

$$C_c = C_Q - C_i \quad \text{for SENB, CT} \quad (5)$$

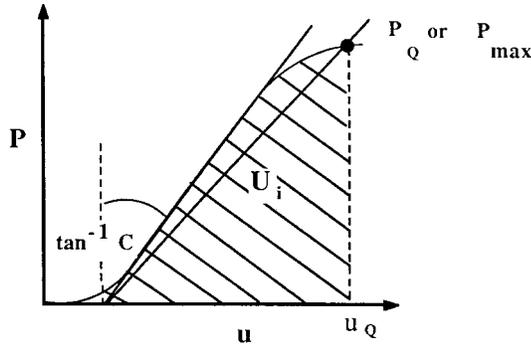

a) LOAD - DEFLECTION IN FRACTURE TEST

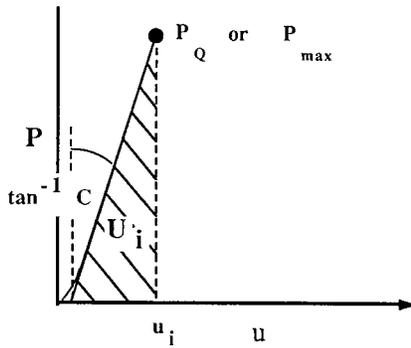

b) LOAD - DEFLECTION IN INDENTATION
FIG. 6 Method of Correcting for Indentation

TABLE 1 Calibration Factors SENB^A S/W = 4

a/W	f(x)	φ	Ψ	η _e
0.450	9.14	0.274	45.8	2.00
0.455	9.27	0.272	46.7	2.00
0.460	9.41	0.269	47.6	2.01
0.465	9.55	0.266	48.5	2.01
0.470	9.70	0.263	49.5	2.02
0.475	9.85	0.260	50.4	2.02
0.480	10.00	0.257	51.4	2.03
0.485	10.16	0.254	52.5	2.03
0.490	10.32	0.252	53.5	2.03
0.495	10.48	0.249	54.7	2.03
0.500	10.65	0.246	55.8	2.03
0.505	10.82	0.243	57.0	2.03
0.510	10.99	0.241	58.2	2.04
0.515	11.17	0.238	59.4	2.04
0.520	11.36	0.236	60.7	2.04
0.525	11.54	0.233	62.1	2.04
0.530	11.74	0.230	63.5	2.04
0.535	11.94	0.228	64.9	2.04
0.540	12.14	0.225	66.4	2.04
0.545	12.35	0.223	67.9	2.04
0.550	12.56	0.220	69.5	2.05

^A Values calculated using A. Bakker, Compatibility Compliance and Stress Intensity Expressions for the Standard Three-Point Bend Specimens. Paper submitted for publication in *International Journal of Fatigue and Fracture of Engineering Materials and Structures* (March 1989).

10. Report

10.1 List the information required to perform the test and the results obtained in the form of a table. The form to use is provided in Table 3.

TABLE 2 Calibration Factors Compact Tension^A

a/W	f(x)	φ	Ψ	η _e
0.450	8.34	0.208	28.9	2.64
0.455	8.45	0.207	29.6	2.63
0.460	8.57	0.207	30.4	2.61
0.465	8.70	0.206	31.1	2.60
0.470	8.83	0.205	31.9	2.58
0.475	8.96	0.204	32.7	2.57
0.480	9.09	0.203	33.5	2.56
0.485	9.23	0.202	34.4	2.54
0.490	9.36	0.201	35.3	2.53
0.495	9.51	0.200	35.3	2.53
0.500	9.65	0.199	37.1	2.51
0.505	9.81	0.198	38.0	2.50
0.510	9.96	0.197	39.0	2.49
0.515	10.12	0.196	40.0	2.48
0.520	10.28	0.194	41.1	2.47
0.525	10.45	0.193	42.1	2.46
0.530	10.62	0.192	43.3	2.45
0.535	10.80	0.190	44.4	2.44
0.540	10.98	0.189	45.6	2.43
0.545	11.17	0.188	46.8	2.42
0.550	11.36	0.186	48.1	2.41

^A Values calculated using J. A. Knapp, G. S. Leger and B. Gross, Fracture Mechanics Sixteenth Symposium, *ASTM, STP 868*, 19, pp. 27-44.

TABLE 3 Testing Summary

Fracture Test Parameters	
Testing laboratory	
Materials/orientation	
Specimen geometry	
Test temperature, °C	
Loading rate, m/s	
Notching method	
Specimen number	
Width (W), mm	
Crack length from 7.2.2, mm	
P _{max} , N	
P _{max} loading rate, s	
P _Q , N	
P _Q loading time, s	
Stable or unstable growth	
K _Q , MPa · m ^{1/2}	
Uncorrected energy, J	
Corrected energy, J	
G _{IC} , kJ/m ²	
Tensile Test Parameters	
σ _y , MPa	
σ _y loading time, s	
Validity Checks	
P _{max} /P _Q	
2.5 (K _Q /σ _y) ²	
E/(1 - ν ²) via C, MPa	
E/(1 - ν ²) via K _Q ² /G _{IC} , MPa	

11. Precision and Bias

11.1 Table 4 is based on a round robin conducted in 1988 in

TABLE 4 Precision Statistics from Round-Robin Study in Accordance with Practice E 691

Material ^A	Average	S _x	S _r	S _R	r	R
A	4.34	0.652	0.235	0.679	0.658	1.90
B	5.70	1.420	0.618	1.510	1.730	4.23
C	3.60	0.692	0.343	0.747	0.960	2.09
D	5.90	1.950	0.944	2.100	2.640	7.39

^A Material A is values of K_{IC} for nylon. Material B is values of G_{IC} for nylon. Material C is values of K_{IC} for polycarbonate. Material D is values of G_{IC} for polycarbonate. Units for all columns are as follows: K_{IC} in units of MPa · m^{1/2}. G_{IC} in units of kJ/m².

accordance with Practice E 691, involving four materials tested by nine laboratories. For each material, all the samples were prepared at one source, but the individual specimens were prepared at the laboratories which tested them. Each test result was the average of three individual determinations. Each laboratory obtained one test result for each material.

NOTE 5—The following explanations of r and R (11.2-11.2.3) are only intended to present a meaningful way of considering the approximate precision of this test method. The data in Table 4 should not be rigorously applied to acceptance or rejection of material, as those data are specific to the round robin and may not be representative of other lots, conditions, materials, or laboratories. Users of this test method should apply the principles outlined in Practice E 691 to generate the data specific to their laboratory and materials, or between specific laboratories. The principles of 11.2-11.2.3 would then be valid for such data.

11.2 *Concept of r and R* —If S_r and S_R have been calculated from a large enough body of data, and for test results that were averages from testing three specimens, the information in 11.2.1-11.2.3 applies.

11.2.1 *Repeatability, r* (comparing two test results for the same material, obtained by the same operator using the same equipment on the same day)—The two test results should be judged not equivalent if they differ by more than the r value for that material.

11.2.2 *Reproducibility, R* (comparing two test results for the same material, obtained by different operators using different equipment on the same day)—The two test results should be judged not equivalent if they differ by more than the R value for that material.

11.2.3 Any judgement in accordance with 11.2.1 or 11.2.2 would have an approximate 95 % (0.95) probability of being correct.

11.3 *Bias*—There are no recognized standards by which to estimate bias of these test methods.

12. Keywords

12.1 critical-strain energy release rate; energy-to-break; fracture toughness; plane-strain fracture toughness

ANNEXES

(Mandatory Information)

A1. SPECIAL REQUIREMENTS FOR THE TESTING OF SINGLE-EDGE NOTCH-BEND SPECIMENS

A1.1 Specimen

A1.1.1 The standard bend specimen is a single edge-notched beam loaded in three-point bending with a support span, S , nominally equal to four times the width, W . The general proportions of this specimen configuration are shown in Fig. 3(a).

A1.1.2 Alternative specimens may have $2 < W/B < 4$. These specimens shall also have a nominal support span S , equal to $S = 4W$.

A1.1.3 *Specimen Preparation*—For generally applicable specifications concerning specimen size and preparation see 7.1.

A1.2 Apparatus

A1.2.1 *Bend-Test Fixture*—The general principles of the bend-test fixture are illustrated in Fig. 1. This fixture is designed to minimize frictional effects by allowing the support rollers to rotate and move apart slightly as the specimen is loaded, thus permitting rolling contact. Thus, the support rollers are allowed limited motion along the plane surfaces parallel to the notched side of the specimen, but are initially positively positioned against stops that set the span length and are held in place by low-tension springs (such as rubber bands).

A1.2.2 *Displacement Gage*—For generally applicable details concerning the displacement gage, see 6.2. For the bend specimen the displacements will be essentially independent of the gage length up to a gage length of $W/2$.

A1.3 Procedure

A1.3.1 *Measurement*—For a bend specimen measure the width, W , and the crack length, a , from the notched side of the

specimen to the opposite side and to the crack front, respectively.

A1.3.1.1 For general requirements concerning specimen preparation see 7.4.

A1.3.2 *Bend Specimen Testing*—Set up the test fixture so that the line of action of the applied load shall pass midway between the support roll centers within 1 % of the distance between these centers. Measure the span, S , to within 0.5 % of nominal length. Locate the specimen with the crack tip midway between the rolls within 1 % of the span, and square to the roll axes within 2°.

A1.3.2.1 Load the specimen at a rate of 10 mm/min, as suggested in 8.3.1.

NOTE A1.1—A loading rate of 12.5 mm/min (0.5 in./min) may be used if this is the only rate available.

A1.4 Calculation

A1.4.1 *Interpretation of Test Record*—For general requirements and procedures in interpretation of the test record, see 9.1.

A1.4.2 *Validity Requirements*—For a description of the validity requirements in terms of limitations on P_{\max}/P_Q and the specimen size requirements, see 9.1.1.

A1.4.3 *Calculations of K_Q* —The general formula for K_Q calculation of bend specimens is given in (3). For bend specimens with $S/W = 4$ (Note A1.2), K_Q in units of $\text{MPa} \cdot \text{m}^{1/2}$ is as follows:

$$K_Q = \left(\frac{P_Q}{BW^{3/2}} \right) f(x)$$

where ($0 < x < 1$):

$$f(x) = 6x^{1/2} \frac{[1.99 - x(1-x)(2.15 - 3.93x + 2.7x^2)]}{(1+2x)(1-x)^{3/2}} \quad (\text{A1.1})$$

and:

- P_Q = load as determined in 9.1.1, kN,
 B = specimen thickness as determined in 8.2.1, cm,
 W = specimen depth (width) as determined in 8.2.3, cm,
 and
 a = crack length as determined in 8.2.2, cm.

$$x = a/W$$

Tabulated values of $f(x)$ are given in Table 1.

NOTE A1.2—The expression in A1.4.3 is considered to be accurate within $\pm 0.5\%$ over the entire range of x from 0 to 1 for an $S/W = 4$ (6).

A1.4.4 *Calculation of G_Q* —For the bend specimens calculate G_Q in units of kJ/m^2 from the corrected energy, U , as follows:

$$G_Q = U/(BW\phi) \quad \text{or} \quad G_Q = \eta_e U/[B(W-a)] \quad (\text{A1.2})$$

A2. SPECIAL REQUIREMENTS FOR THE TESTING OF COMPACT-TENSION SPECIMENS

A2.1 Specimen

A2.1.1 The standard compact-tension specimen is a single edge-notched plate loaded in tension. The general proportions of this specimen configuration are shown in Fig. 3(b).

A2.1.2 Alternative specimens may have $2 \leq W/B \leq 4$ but with no change in other proportions.

A2.2 Specimen Preparation

A2.2.1 For generally applicable specifications concerning specimen size and preparation, see 7.1.

A2.3 Apparatus

A2.3.1 *Tension-Testing Clevis*—A loading clevis suitable for testing compact tension specimens is shown in Fig. 2. Both ends of the specimen are held in such a clevis and loaded through pins in order to permit rotation of the specimen during testing. In order to provide rolling contact between the loading pins and the clevis holes, these holes are provided with small flats on the loading surfaces. Other clevis designs may be used if it can be demonstrated that they will accomplish the same result as the design shown.

A2.3.1.1 The critical tolerances and suggested proportions of the clevis and pins are given in Fig. 2. These proportions are based on specimens having $W/B = 2$ for $B > 12.7$ mm and $W/B = 4$ for $B < 12.7$ mm.

A2.3.1.2 Careful attention should be given to achieving as good alignment as possible through careful machining of all auxiliary gripping fixtures.

A2.4 Procedure

A2.4.1 *Measurement*—For a compact-tension specimen measure the width, W , and the crack length, a , from the plane of the centerline of the loading holes (the notched edge is a convenient reference line, but the distance from the centerline of the holes to the notched edge must be subtracted to determine W and a). Measure the width, W , to the nearest 0.025

mm, at not less than three positions near the notch location, and record the average value.

Values of η_e are given in Table 1. The energy calibration factor, ϕ , is defined as:

$$\phi = C[dC/d(A/W)] \quad (\text{A1.3})$$

and may be computed from the following:

$$\phi = \frac{A + 18.64}{dA/dx} \quad (\text{A1.4})$$

where:

$$\begin{aligned} A &= [16x^2/(1-x)^2][8.9 - 33.717x + 79.616x^2 \\ &\quad - 112.952x^3 + 84.815x^4 - 25.672x^5], \text{ and} \\ dA/dx &= [16x^2/(1-x)^2][-33.717 + 159.232x \\ &\quad - 338.856x^2 + 339.26x^3 - 128.36x^4] \\ &\quad + 16[8.9 - 33.717x + 79.616x^2 \\ &\quad - 112.952x^3 + 84.815x^4 - 25.672x^5] \\ &\quad \{[2x(1-x) + 2x^2]/(1-x)^3\} \end{aligned}$$

Values of ϕ are given in Table 1.

mm, at not less than three positions near the notch location, and record the average value.

A2.4.1.1 For general requirements concerning specimen preparation see 7.4.

A2.4.2 *Compact-Tension-Specimen Testing*—When assembling the loading train (clevises and their attachments to the tensile machine) care should be taken to minimize eccentricity of loading due to misalignments external to the clevises. To obtain satisfactory alignment keep the centerline of the upper and lower loading rods coincident within 0.76 mm during the test and center the specimen with respect to the clevis opening within 0.76 mm.

A2.4.2.1 Load the compact-tension-specimen at a rate as specified in 8.3.1.

A2.5 Calculation

A2.5.1 For general requirements and procedures in interpretation of the test record see 9.1.

A2.5.2 For a description of the validity requirements in terms of limitations on P_{\max}/P_Q and the specimen-size requirements see 9.1.

A2.5.3 *Calculations of K_Q* —For the compact-tension specimens calculate K_Q in units of $\text{MPa}\cdot\text{m}^{1/2}$ from the following expression (see Note A2.1).

$$K_Q = (P_Q/BW^{1/2})f(x) \quad (\text{A2.1})$$

where ($0.2 < x < 0.8$):

$$f(x) = \frac{(2+x)(0.886 + 4.64x - 13.32x^2 + 14.72x^3 - 5.6x^4)}{(1-x)^2}$$

where:

- P_Q = load as determined in 9.1.1, kN,
 B = specimen thickness as determined in 8.2.1, cm,
 W = specimen width as determined in A2.4.1, cm,
 a = crack length as determined in 8.2.2, cm, and

$$x = a/W.$$

Values of $f(x)$ are given in Table 2.

NOTE A2.1—The expression in A2.5.3 is considered to be accurate within $\pm 0.65\%$ over the range of a/W from 0.2 to 1 (6).

A2.6 *Calculation of G_Q* —For the compact tension specimens calculate G_Q in units of kJ/m^2 from the corrected energy, U , as follows:

$$G_Q = U/(BW\phi) \quad \text{or} \quad G_Q = \eta_e U/[B(W-a)] \quad (\text{A2.2})$$

The energy-calibration factor, ϕ , may be computed from

$$\phi = \frac{(1.9118 + 19.118x - 2.5122x^2 - 23.226x^3 + 20.54x^4)(1-x)}{(19.118 - 5.0244x - 69.678x^2 + 82.16x^3)(1-x) + 2(1.9118 + 19.118x - 2.5122x^2 - 23.226x^3 + 20.54x^4)}$$

Values of ϕ and η_e are given in Table 2.

REFERENCES

- (1) Brown, W. F., Jr., and Srawley, J. E., "Plane Strain Crack Toughness Testing of High Strength Metallic Materials," *ASTM STP 410*, ASTM, 1966, p. 1.
- (2) "Fracture Toughness Testing and Its Applications," *ASTM STP 381*, ASTM, April 1965, p. 30.
- (3) Srawley, J. E., "Wide Range Stress Intensity Factor Expressions for ASTM E399 Standard Fracture Toughness Specimens," *International Journal of Fracture Mechanics*, Vol 12, June 1976, p. 475.
- (4) Newman, J. C., "Stress Analysis of Compact Specimens Including the Effects of Pin Loading," *ASTM STP 560*, ASTM, 1974, p. 105.
- (5) Williams, J. G., "Fracture Mechanics of Polymers," Ellis Horwood/Wiley, 1985.
- (6) Towers, O. L., "Stress Intensity Factors, Compliances and Elastic η_e Factors for Six Test Geometries," *The Welding Institute*, March 1981.

SUMMARY OF CHANGES

This section identifies the location of selected changes to these test methods. For the convenience of the user, Committee D-20 has highlighted those changes that may impact the use of these test methods. This section may also include descriptions of the changes or reasons for the changes, or both.

D 5045–99:

(1) Revised A1.4.3.

(2) Added Summary of Changes.

The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, 100 Barr Harbor Drive, West Conshohocken, PA 19428.